

UDDEHOLM DIEVAR

Uddeholm Dievar is a specially developed steel grade by Uddeholm, which provides the best possible performance.

The chemical composition and the very latest in production technique make the property profile outstanding. The combination of excellent toughness and very good hot strength gives Uddeholm Dievar a very good heat checking- and gross cracking resistance.

The steel is suitable in high demand hot work applications like die casting, forging and extrusion. The property profile makes it also suitable in other applications, e.g. plastics and High Performance Steel.

Uddeholm Dievar offers the potential for significant improvements in die life, thereby improving the tooling economy.

This information is based on our present state of knowledge and is intended to provide general notes on our products and their uses. It should not therefore be construed as a warranty of specific properties of the products described or a warranty for fitness for a particular purpose.

Classified according to EU Directive 1999/45/EC

For further information see our "Material Safety Data Sheets".

Edition 8, 01.2011

The latest revised edition of this brochure is the English version, which is always published on our web site www.uddeholm.com



SS-EN ISO 9001
SS-EN ISO 14001

General

Uddeholm Dievar is a high performance chromium-molybdenum-vanadium alloyed hot work tool steel which offers a very good resistance to heat checking, gross cracking, hot wear and plastic deformation. Uddeholm Dievar is characterized by:

- Excellent toughness and ductility in all directions
- Good temper resistance
- Good high-temperature strength
- Excellent hardenability
- Good dimensional stability throughout heat treatment and coating operations

Riktanalys	C 0.35	Si 0.2	Mn 0.5	Cr 5.0	Mo 2.3	V 0.6
Standard specification	None					
Delivery condition	Soft annealed to approx. 160 HB					
Colour code	Yellow/grey					

Improved tooling performance

Uddeholm Dievar is a premium hot work tool steel developed by Uddeholm. It is manufactured utilizing the very latest in production and refining techniques. The Uddeholm Dievar development has yielded a die steel with the ultimate resistance to heat checking, gross cracking, hot wear and plastic deformation. The unique properties profile for Uddeholm Dievar makes it the best choice for die casting, forging and extrusion.



Hot work applications

Heat checking is one of the most common failure mechanism e.g. in die casting and now days also in forging applications. Uddeholm Dievar's superior ductility yields the highest possible level of heat checking resistance. With Uddeholm Dievar's outstanding toughness and hardenability the resistance to heat checking can further be improved. If gross cracking is not a factor then a higher working hardness can be utilized (+2 HRC).

Regardless of the dominant failure mechanism; e.g. heat checking, gross cracking, hot wear or plastic deformation. Uddeholm Dievar offers the potential for significant improvements in die life and then resulting in better tooling economy.

Uddeholm Dievar is the material of choice for the high demand die casting-, forging- and extrusion industries.

Tools for die casting

Part	Aluminium, magnesium alloys
Dies	44–50 HRC

Tools for extrusion

Part	Copper, copper alloys HRC	Aluminium, magnesium alloys HRC
Dies	–	46–52
Liners, dummy blocks, stems	46–52	44–52

Tools for hot forging

Part	Steel, Aluminium
Inserts	44–52 HRC

Properties

The reported properties are representative of samples which have been taken from the centre of a 610 x 203 mm (24" x 8") bar. Unless otherwise is indicated all specimens have been hardened at 1025°C (1875°F), quenched in oil and tempered twice at 615°C (1140°F) for two hours; yielding a working hardness of 44–46 HRC.

Physical properties

Data at room and elevated temperatures.

Temperature	20°C (68°F)	400°C (750°F)	600°C (1110°F)
Density, kg/m ³ lbs/in ³	7 800 0.281	7 700 0.277	7 600 0.274
Modulus of elasticity MPa psi	210 000 30.5 × 10 ⁶	180 000 26.1 × 10 ⁶	145 000 21.0 × 10 ⁶
Coefficient of thermal expansion per °C from 20°C per °F from 68°F	–	12.7 × 10 ⁻⁶ 7.0 × 10 ⁻⁶	13.3 × 10 ⁻⁶ 7.3 × 10 ⁻⁶
Thermal conductivity W/m °C Btu in/(ft ² h °F)	–	31 216	32 223


Mechanical properties

Tensile properties at room temperature, short transverse direction.

Hardness	44 HRC	48 HRC	52 HRC
Tensile strength R _m	1480 MPa 96 tsi 214 000 psi	1640 MPa 106 tsi 237 000 psi	1900 MPa 123 tsi 275 000 psi
Yield strength R _{p0,2}	1210 MPa 78 tsi 175 000 psi	1380 MPa 89 tsi 200 000 psi	1560 MPa 101 tsi 226 000 psi
Elongation A ₅	13 %	13 %	12,5 %
Reduction of area Z	55 %	55 %	52 %

TENSILE PROPERTIES AT ELEVATED TEMPERATURE


Short transverse direction.

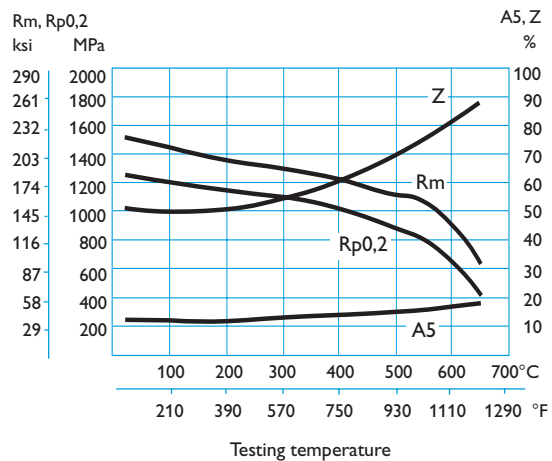

Minimum average unnotched impact ductility is 300 J (220 ft lbs) in the short transverse direction at 44–46 HRC.


CHARPY V-NOTCH IMPACT TOUGHNESS AT ELEVATED TEMPERATURE

Short transverse direction.

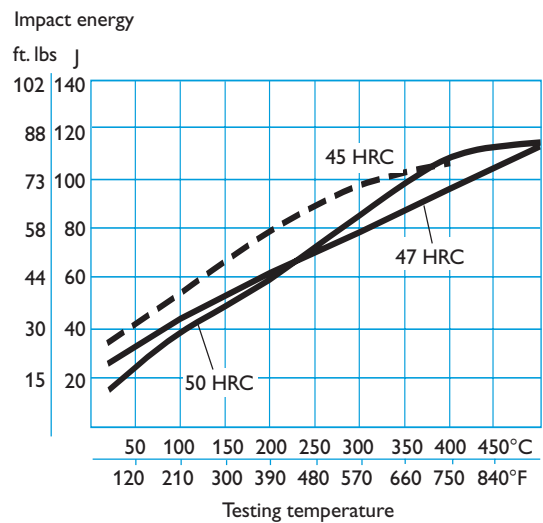

TEMPER RESISTANCE

The specimens have been hardened and tempered to 45 HRC and then held at different temperatures from 1 to 100 hours.

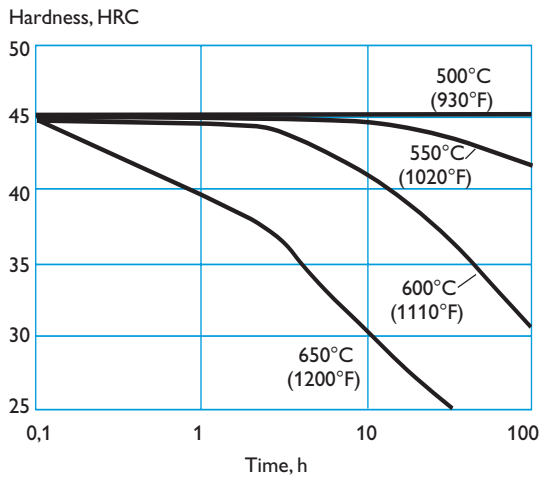

Heat treatment—general recommendations

Soft annealing

Protect the steel and heat through to 850°C (1560°F). Then cool in furnace at 10°C (20°F) per hour to 600°C (1110°F), then freely in air.

Stress relieving

After rough machining the tool should be heated through to 650°C (1200°F), holding time 2 hours. Cool slowly to 500°C (930°F), then freely in air.

Hardening

Preheating temperature: 600–900°C (1110–1650°F). Normally a minimum of two preheats, the first in the 600–650°C (1110–1200°F) range, and the second in the 820–850°C (1510–1560°F) range. When three preheats are used the second is carried out at 820°C (1510°F) and the third at 900°C (1650°F).

Austenitizing temperature: 1000–1030°C (1830–1890°F).


Temperature		Soaking time* minutes	Hardness before tempering
°C	°F		
1000	1830	30	52 ± 2 HRC
1025	1875	30	55 ± 2 HRC

* Soaking time = time at hardening temperature after the tool is fully heated through


Protect the tool against decarburization and oxidation during austenitizing.

CCT GRAPH

Austenitizing temperature 1025°C (1875°F). Holding time 30 minutes.

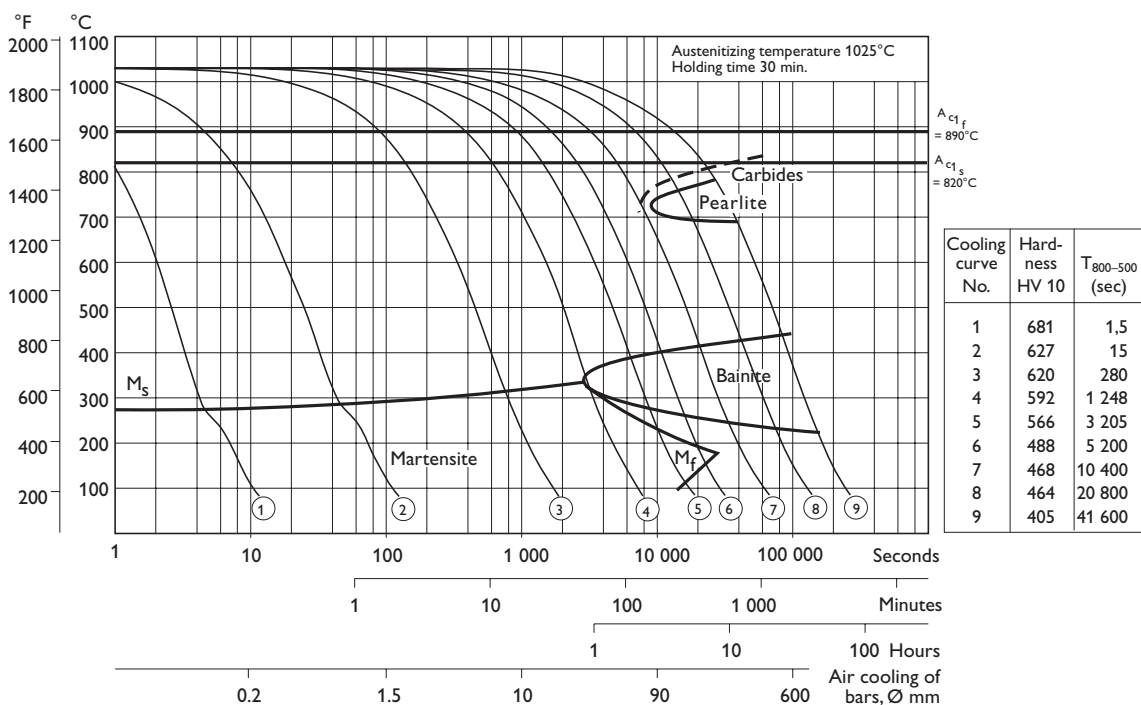

HARDNESS, GRAIN SIZE AND RETAINED AUSTENITE AS FUNCTIONS OF AUSTENITIZING TEMPERATURE

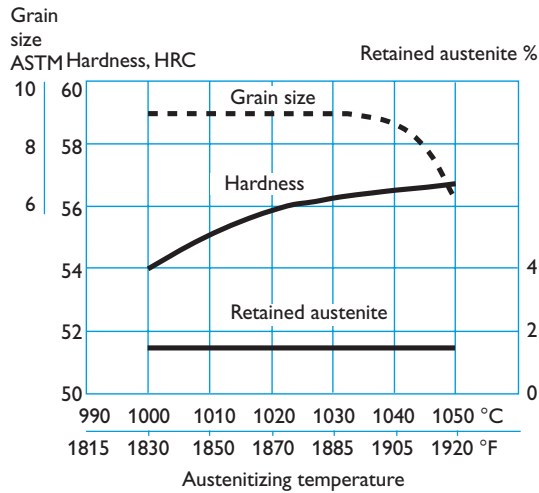

Quenching

As a general rule, quench rates should be as rapid as possible. Accelerated quench rates are required to optimize tool properties specifically with regards to toughness and resistance to gross cracking. However, risk of excessive distortion and cracking must be considered.

QUENCHING MEDIA

The quenching media should be capable of creating a fully hardened microstructure. Different quench rates for Uddeholm Dievar are defined by the CCT graph, page 5.

RECOMMENDED QUENCHING MEDIA

- High speed gas/circulating atmosphere
- Vacuum (high speed gas with sufficient positive pressure). An interrupted quench at 320–450°C (610–840°F) is recommended where distortion control and quench cracking are a concern
- Martempering bath, salt bath or fluidized bed at 450–550°C (840–1020°F)
- Martempering bath, salt bath or fluidized bed at 180–200°C (360–390°F)
- Warm oil, approx. 80°C (180°F)


Note: Temper the tool as soon as its temperature reaches 50–70°C (120–160°F).

Tempering

Choose the tempering temperature according to the hardness required by reference to the tempering graph below. Temper minimum three times for die casting dies and minimum twice for forging and extrusion tools with intermediate cooling to room temperature. Holding time at temperature minimum 2 hours.


Tempering in the range of 500–550°C (930–1020°F) for the intended final hardness will result in a lower toughness.

TEMPERING GRAPH

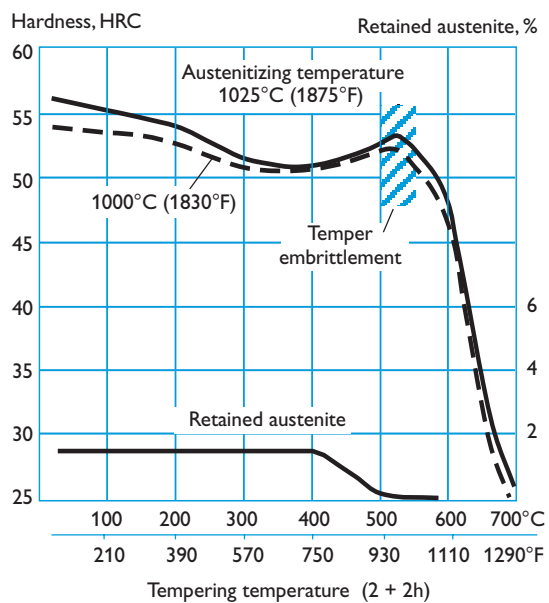

EFFECT OF TEMPERING TEMPERATURE ON ROOM TEMPERATURE CHARPY V NOTCH IMPACT ENERGY

Short transverse direction.

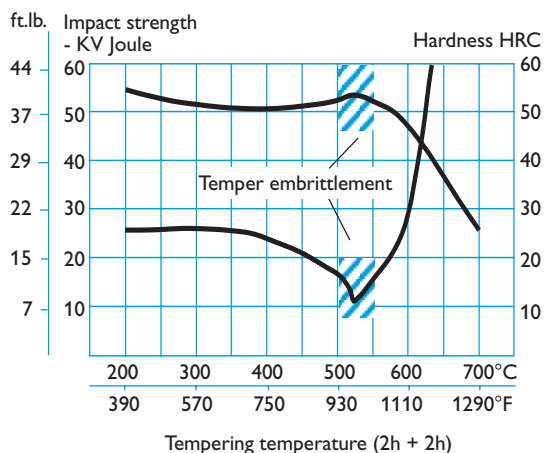

Dimensional changes during hardening and tempering

During hardening and tempering the tool is exposed to both thermal and transformation stresses. These stresses will result in distortion. Insufficient levels of machine stock may result in slower than recommended quench rates during heat treatment. In order to predict maximum levels of distortion with a proper quench, a stress relief is always recommended between rough and semi-finish machining, prior to hardening.

For a stress relieved Uddeholm Dievar tool a minimum machine stock of 0.3% is recommended to account for acceptable levels of distortion during a heat treatment with a rapid quench.

Nitriding and nitrocarburizing

Nitriding and nitrocarburizing result in a hard surface layer which has the potential to improve resistance to wear and soldering, as well as resistance to premature heat checking. Uddeholm Dievar can be nitrided and nitrocarburized via a plasma, gas, fluidized bed, or salt process. The temperature for the deposition process should be minimum 25–50°C (50–90°F) below the highest previous tempering temperature, depending upon the process time and temperature. Otherwise a permanent loss of core hardness, strength, and/or dimensional tolerances may be experienced.

During nitriding and nitrocarburizing, a brittle compound layer, known as the white layer, may be generated. The white layer is very brittle and may result in cracking or spalling when exposed to heavy mechanical or thermal loads. As a general rule the white layer formation must be avoided.



Nitriding in ammonia gas at 510°C (950°F) or plasma nitriding at 480°C (895°F) both result in a surface hardness of approx. 1100 HV_{0.2}.

In general, plasma nitriding is the preferred method because of better control over nitrogen potential. However, careful gas nitriding can give same results.

The surface hardness after nitrocarburizing in either gas or salt bath at 580°C (1075°F) is approx. 1100 HV_{0.2}.

Depth of nitriding

Process	Time	Depth*	Hardness HV _{0.2}
Gas nitriding at 510°C (950°F)	10 h	0.16 mm 0.0063 inch	1100
	30 h	0.22 mm 0.0087 inch	1100
Plasma nitriding at 480°C (895°F)	10 h	0.15 mm 0.0059 inch	1100
Nitrocarburizing – in gas at 580°C (1075°F) – in salt bath at 580°C (1075°F)	2 h	0.13 mm 0.0051 inch	1100
	1 h	0.08 mm 0.0031 inch	1100

* Depth of case = distance from surface where hardness is 50 HV_{0.2} over base hardness

Cutting data recommendations

The cutting data below are to be considered as guiding values which must be adapted to existing local condition.

The recommendations, in following tables, are valid for Uddeholm Dievar in soft annealed condition approx. 160 HB.

Turning

Cutting data parameters	Turning with carbide		Turning with high speed steel Fine turning
	Rough turning	Fine turning	
Cutting speed (v_c) m/min f.p.m.	150–200 490–655	200–250 655–820	15–20 50–65
Feed (f) mm/r i.p.r.	0.2–0.4 0.008–0.016	0.05–0.2 0.002–0.008	0.05–0.3 0.002–0.012
Depth of cut (a_p) mm inch	2–4 0.08–0.16	0.5–2 0.02–0.08	0.5–2 0.02–0.08
Carbide designation ISO US	P20–P30 C6–C5 Coated carbide	P10 C7 Coated carbide or cermet	– –

Milling

FACE- AND SQUARE SHOULDER MILLING

Cutting data parameters	Milling with carbide	
	Rough milling	Fine milling
Cutting speed (v_c) m/min f.p.m.	130–180 430–590	180–220 590–720
Feed (f_z) mm/tooth inch/tooth	0.2–0.4 0.008–0.016	0.1–0.2 0.004–0.008
Depth of cut (a_p) mm inch	2–4 0.08–0.16	–2 –0.08
Carbide designation ISO US	P20–P40 C6–C5 Coated carbide	P10 C7 Coated carbide or cermet

END MILLING

Cutting data parameters	Type of milling		
	Solid carbide	Carbide indexable insert	High speed steel
Cutting speed (v_c) m/min f.p.m.	130–170 425–560	120–160 390–520	25–30 ¹⁾ 80–100 ¹⁾
Feed (f_z) mm/tooth inch/tooth	0.03–0.20 ²⁾ 0.001–0.008 ²⁾	0.08–0.20 ²⁾ 0.003–0.008 ²⁾	0.05–0.35 ²⁾ 0.002–0.014 ²⁾
Carbide designation ISO US	–	P20–P30 C6–C5	– –

¹⁾ For coated HSS end mill $v_c = 45–50$ m/min. (150–160 f.p.m.)

²⁾ Depending on radial depth of cut and cutter diameter

Drilling

HIGH SPEED STEEL TWIST DRILL

Drill diameter		Cutting speed (v_c)		Feed (f)	
mm	inch	m/min	f.p.m.	mm/r	i.p.r.
– 5	–3/16	15–20*	49–66*	0.05–0.15	0.002–0.006
5–10	3/16–3/8	15–20*	49–66*	0.15–0.20	0.006–0.008
10–15	3/8–5/8	15–20*	49–66*	0.20–0.25	0.008–0.010
15–20	5/8–3/4	15–20*	49–66*	0.25–0.35	0.010–0.014

* For coated HSS drill $v_c = 35–40$ m/min. (110–130 f.p.m.)

CARBIDE DRILL

Cutting data parameters	Type of drill		
	Indexable insert	Solid carbide	Carbide tip ¹⁾
Cutting speed (v_c) m/min f.p.m.	180–220 590–720	120–150 390–490	60–90 195–295
Feed (f) mm/r i.p.r.	0.05–0.25 ²⁾ 0.002–0.01 ²⁾	0.10–0.25 ²⁾ 0.004–0.01 ²⁾	0.15–0.25 ²⁾ 0.006–0.01 ²⁾

¹⁾ Drill with replaceable or brazed carbide tip

²⁾ Depending on drill diameter

Cutting data recommendations

The cutting data below should be considered as guidelines only. These guidelines must be adapted to local machining conditions.

The recommendations, in following tables, are valid for Uddeholm Dievar hardened and tempered to 44–46 HRC.

Turning

Cutting data parameters	Turning with carbide	
	Rough turning	Fine turning
Cutting speed (v_c) m/min f.p.m.	40–60 130–195	70–90 230–295
Feed (f) mm/r i.p.r.	0.2–0.4 0.008–0.016	0.05–0.2 0.002–0.008
Depth of cut (a_p) mm inch	1–2 0.04–0.08	0.5–1 0.02–0.04
Carbide designation ISO US	P20–P30 C6–C5 Coated carbide	P10 C7 Coated carbide or mixed ceramic

Drilling

HIGH SPEED STEEL TWIST DRILL (TiCN COATED)

Drill diameter		Cutting speed (v_c)		Feed (f)	
mm	inch	m/min	f.p.m.	mm/r	i.p.r.
– 5	–3/16	4–6	13–20	0.05–0.10	0.002–0.004
5–10	3/16–3/8	4–6	13–20	0.10–0.15	0.004–0.006
10–15	3/8–5/8	4–6	13–20	0.15–0.20	0.006–0.008
15–20	5/8–3/4	4–6	13–20	0.20–0.30	0.008–0.012

CARBIDE DRILL

Cutting data parameters	Type of drill		
	Indexable insert	Solid carbide	Carbide tip ¹⁾
Cutting speed (v_c) m/min f.p.m.	60–80 195–260	60–80 195–260	40–50 130–160
Feed (f) mm/r i.p.r.	0.05–0.25 ²⁾ 0.002–0.01 ²⁾	0.10–0.25 ²⁾ 0.004–0.01 ²⁾	0.15–0.25 ²⁾ 0.006–0.01 ²⁾

¹⁾ Drill with replaceable or brazed carbide tip

²⁾ Depending on drill diameter

Milling

FACE- AND SQUARE SHOULDER MILLING

Cutting data parameters	Milling with carbide	
	Rough milling	Fine milling
Cutting speed (v_c) m/min f.p.m.	50–90 160–295	90–130 295–425
Feed (f_z) mm/tooth inch/tooth	0.2–0.4 0.008–0.016	0.1–0.2 0.004–0.008
Depth of cut (a_p) mm inch	2–4 0.08–0.16	–2 –0.08
Carbide designation ISO US	P20–P40 C6–C5 Coated carbide	P10 C7 Coated carbide or cermet

END MILLING

Cutting data parameters	Type of milling		
	Solid carbide	Carbide indexable insert	High speed steel TiCN coated
Cutting speed (v_c) m/min f.p.m.	60–80 195–260	70–90 230–295	5–10 16–33
Feed (f_z) mm/tooth inch/tooth	0.03–0.20 ¹⁾ 0.001–0.008 ¹⁾	0.08–0.20 ¹⁾ 0.003–0.008 ¹⁾	0.05–0.35 ¹⁾ 0.002–0.014 ¹⁾
Carbide designation ISO US	–	P10–P20 C6–C5	– –

¹⁾ Depending on radial depth of cut and cutter diameter

Grinding

A general grinding wheel recommendation is given below. More information can be found in the Uddeholm publication “Grinding of Tool Steel”.

WHEEL RECOMMENDATION

Type of grinding	Soft annealed condition	Hardened condition
Face grinding straight wheel	A 46 HV	A 46 HV
Face grinding segments	A 24 GV	A 36 GV
Cylindrical grinding	A 46 LV	A 60 KV
Internal grinding	A 46 JV	A 60 IV
Profile grinding	A 100 LV	A 120 JV

Electrical Discharge Machining—EDM

Following the EDM process, the applicable die surfaces are covered with a resolidified layer (white layer) and a rehardened and untempered layer, both of which are very brittle and hence detrimental to die performance. If EDM is used the white layer must be completely removed mechanically by grinding or stoning. After the finish machining the tool should also then be given an additional temper at approx. 25°C (50°F) below the highest previous tempering temperature.

Further information is given in the Uddeholm brochure “EDM of Tool Steel”.

Further information

Please contact your local Uddeholm office for further information on the selection, heat treatment, application and availability of Uddeholm tool steels.

Welding

Welding of die components can be performed, with acceptable results, as long as the proper precautions are taken during the preparation of the joint, the filler material selection, the preheating of the die, the controlled cooling of the die and the post weld heat treatment processes. The following guidelines summarize the most important welding process parameters.

For more detailed information refer to the Uddeholm brochure “Welding of Tool Steel”.

Welding method	TIG	MMA
Preheating temperature*	325–375°C (620–710°F)	325–375°C (620–710°F)
Filler metals	DIEVAR TIG-Weld QRO 90 TIG-Weld	QRO 90 Weld
Maximum interpass temperature	475°C (880°F)	475°C (880°F)
Post welding cooling	20–40°C/h (35–70°F/h) for the first 2–3 hours and then freely in air.	
Hardness after welding	48–53 HRC	48–53 HRC
<i>Heat treatment after welding</i>		
Hardened condition	Temper 10–20°C (20–40°F) below the highest previous tempering temperature.	
Soft annealed condition	Soft-anneal the material at 850°C (1560°F) in protected atmosphere. Then cool in the furnace at 10°C (20°F) per hour to 600°C (1110°F) then freely in air.	

* Preheating temperature must be established throughout the die and must be maintained for the entirety of the welding process, to prevent weld cracking



Network of excellence

UDDEHOLM is present on every continent. This ensures you high-quality Swedish tool steel and local support wherever you are. ASSAB is our wholly-owned subsidiary and exclusive sales channel, representing Uddeholm in various parts of the world. Together we secure our position as the world's leading supplier of tooling materials.

UDDEHOLM is the world's leading supplier of tooling materials. This is a position we have reached by improving our customers' everyday business. Long tradition combined with research and product development equips Uddeholm to solve any tooling problem that may arise. It is a challenging process, but the goal is clear – to be your number one partner and tool steel provider.

Our presence on every continent guarantees you the same high quality wherever you are. ASSAB is our wholly-owned subsidiary and exclusive sales channel, representing Uddeholm in various parts of the world. Together we secure our position as the world's leading supplier of tooling materials. We act worldwide, so there is always an Uddeholm or ASSAB representative close at hand to give local advice and support. For us it is all a matter of trust – in long-term partnerships as well as in developing new products. Trust is something you earn, every day.

For more information, please visit www.uddeholm.com, www.assab.com or your local website.

UD
WOR
RUST IS SOM
TRUST IS I
AUTOMOTIVE
KINDING SU
TOUGHNESS ST
MATERIALS M
EDDING WATER
BYSTANDIN
RESULTS M
CUSTOMER B
BILITY TRUST IS
AUTOMOTIVE
LEADING SU
INNOVATION
STRENGTH INNOVATION
WORLDWIDE PRE
SOMETHING YO
PROBLEM
THE WORL
NOMY THE
DUCTILITY TO
COMMITMENT PART
KNOWLEDGE UN
KNOWLEDGE
RELIABILITY
OF EXCEL
AUTOMOTIVE A
ECONOMY THE
TOTAL ECONOMY
DUCTILITY TOUGHNESS
HARDNESS WORLDW
TRUST IS SOMETHING
UNDERSTANDING MACHIN
RESULTS SOLVING PROB
ECONOMY THE WORL
STRENGTH IN
TOUGHNESS STRENGTH I
MATERIALS PARTN
UNDERSTANDING MACHIN
BILITY RELIABILITY RESU
LASTING TOOLS TOTAL
YOU EARN, EVERY DAY. LO
OF THINKING HIGH PE
OFTOOLING MATERIALS C
INNOVATION KNOWLEDGE
STRENGTH INNOVATION KNOW
EXPERIENCE LONG DURABILITY
TRUST IS SOMETHING YOU EARN,
PROBLEMS AUTOMOTIVE